

Observation of tunable exchange bias in $\text{Sr}_2\text{YbRuO}_6$

R. P. Singh and C. V. Tomy

Department of Physics, Indian Institute of Technology Bombay, Mumbai-400076, India.

A. K. Grover

*Department of Condensed Matter Physics and Materials Science,
Tata Institute of Fundamental Research Colaba, Mumbai-400005, India.*

The double perovskite compound, $\text{Sr}_2\text{YbRuO}_6$, displays reversal in the orientation of magnetic moments along with negative magnetization due to an underlying magnetic compensation phenomenon. The exchange bias (EB) field below the compensation temperature could be the usual negative or the positive depending on the initial cooling field. This EB attribute has the potential of getting tuned in a preselected manner, as the positive EB field is seen to crossover from positive to negative value above T_{comp} .

The notion of an exchange bias (EB) field¹, which is exemplified by the identification of a shift² in the centre of gravity of the magnetization hysteresis (M - H) loop, has implications for magnetic read heads³, thermally assisted magnetic random access memories⁴, and other spintronics devices^{5,6}. The EB phenomenon is considered to be a quintessential attribute¹ of a ferromagnetic (FM)/ antiferromagnetic (AFM) composite or a bilayer assembly, when the entire system is cooled below ordering temperature T_N of the AFM part, which lies below the (T_C) of the FM, i.e., $T_N < T_C$. Usually, the EB field is negative as the centre of M - H loop gets left shifted below (T_N)¹. But occasionally the right shift of the loop, i.e., positive exchange bias (PEB) field has also been noted⁷⁻¹². The EB had mostly been observed in magnetic multi-component systems, such as oxidized magnetic nanoparticles, FM/AFM multilayers, FM/spin glass bilayer thin films, etc.¹. However interestingly, in recent years, it has also been noted in several bulk homogenous materials, like, manganites¹³, cobaltates¹⁴ and admixed intermetallic compounds^{15,16}. Recently Kulkarni *et al.*¹⁷ have unearthed EB effect in a single crystal of an admixed rare earth intermetallic compound, $\text{Nd}_{0.75}\text{Ho}_{0.25}\text{Al}_2$, in close proximity to the compensation temperature (T_{comp}) in it. They encountered the sudden surfacing of the PEB on approaching T_{comp} , the EB changed sign on going across it; the sign reversal of exchange bias field is sought to be rationalized in terms of reversal in the nearly balanced local magnetic moment contributions from antiferromagnetically linked Nd^{3+} and Ho^{3+} ions along with that of the conduction electron polarization (CEP), with respect to the applied field direction¹⁷.

We have now studied the EB phenomenon in a double perovskite antiferromagnetic (AFM) insulator $\text{Sr}_2\text{YbRuO}_6$ ¹⁸. This compound belongs to the Ruthenates family, $\text{Sr}_2\text{LnRuO}_6$ ($\text{Ln} = \text{Y}$ or rare earth)¹⁹⁻²¹, and shows interesting magnetic properties below the magnetic ordering temperature, which include the (i) magnetization reversal and (ii) the magnetic compensation characterized by crossover of the magnetization axis ($M = 0$ line) towards the negative magnetization values¹⁸. In the antiferromagnetic Sr_2YRuO_6 compound, containing non-magnetic Y element, the local moment resides on Ru ion alone²², whereas in $\text{Sr}_2\text{YbRuO}_6$, both Yb and Ru ions possess local magnetic moments of $4.54\mu_B$ and $3.87\mu_B$, respectively²³. The monoclinic structure²³ of these AFM insulators facilitates the Dzyaloshinsky-Moria (D-M)

interaction²⁴ between the antiferromagnetically ordered local moments. The anisotropic D-M interaction results in canting of the antiferromagnetically ordered moments and hence a weak residual ferromagnetism germinates^{25,26}. The presence of a weak ferromagnetic component could provide a circumstance analogous to that associated with the FM/AFM composite systems. Though the magnetization reversal, zero magnetization and negative magnetization in $\text{Sr}_2\text{YbRuO}_6$ could be expected from the combined effects of D-M interaction and the unidirectional anisotropy¹⁸, the discovery of the EB and its sign reversal near the compensation temperature and the dependence of sign of EB at low temperature (i.e., below the T_{comp}) on the thermo-magnetic history has brought to light the possibility of tuning of the EB from positive to negative values in a convenient and predictable manner in double perovskite compounds. Such an interesting finding is being reported here; this attribute could be utilized in niche applications in spintronics.

A typical field-cooled (FC) magnetization curve M_{FC} measured at low fields (e.g. at $H = 50$ Oe) in $\text{Sr}_2\text{YbRuO}_6$ is shown in Fig. 1. The sudden increase in the M_{FC} at the onset of the ordering temperature (44 K) is due to the presence of a weak ferromagnetic component¹⁸ in this compound. The start of decrease in magnetization around $T \sim 39$ K is due to the onset of reversal in magnetization of the residual ferromagnetic part. This is triggered by the D-M interaction, as noted earlier in the case of isostructural Sr_2YRuO_6 compound²⁷. On cooling below 39 K, the decrease in magnetization continues and it crosses the $M = 0$ axis at the compensation temperature of ~ 33.5 K (marked as T_{comp}), and magnetization values move towards negative values on further lowering the temperature, signalling the importance of the role of Yb moments in $\text{Sr}_2\text{YbRuO}_6$; no crossover of $M = 0$ axis occurs in Sr_2YRuO_6 ²⁷, where Y^{3+} ions are non-magnetic.

The two insets in Fig. 1 show the M - H loops recorded between ± 50 kOe at 5 K in $\text{Sr}_2\text{YbRuO}_6$ for two typical initial cooling fields, viz., 2 kOe and 50 kOe. At very high fields ($H > 20$ kOe), the M - H response in both the insets of Fig. 1 are quasi-linear, as in antiferromagnets. However, at lower fields (i.e., between ± 20 kOe), one can notice the presence of hysteresis bubbles, with small remnant magnetization ($0.05\mu_B/\text{f.u.}$ of $\text{Sr}_2\text{YbRuO}_6$), which can be attributed to the residual ferromagnetic component originating from a

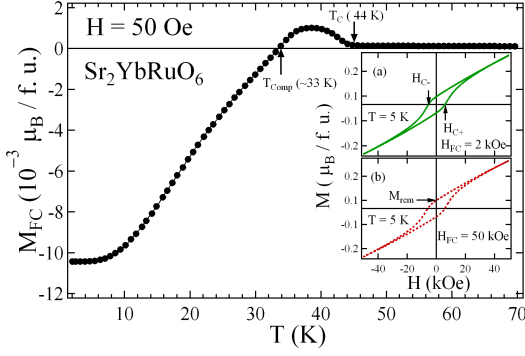


Figure 1: Temperature variation of the field-cooled (FC) magnetization in $H = 50$ Oe in $\text{Sr}_2\text{YbRuO}_6$. The T_C and T_{comp} values have been identified. The insets (a) and (b) show the magnetic hysteresis (M - H) loops traced at 5 K after initial field cooling in (a) $H_{\text{FC}} = 2$ kOe and (b) 50 kOe, respectively.

slight canting of the antiferromagnetically coupled large moments of Yb and Ru ions. There is a subtle but important difference between the two bubbles in the two insets of Fig. 1, which pertains to the shift in the centre of gravity of these bubbles. Figure 2 shows the central portions of two hysteresis bubbles plotted together on an expanded scale, a noticeable difference between the dashed and solid curves as they cross the $M = 0$ axis at a magnetic field (H_- or H_+) can be immediately recognized. The difference between the two loops in Fig. 2 can be characterized in terms of an exchange bias field (H_E), which is usually defined as $H_E = (H_- + H_+)/2$, where H_- and H_+ are the field values at which magnetization axis is crossed during the descending and the ascending field cycles. The loop measured between ± 50 kOe in a cooling field (H_{FC}) of 2 kOe shows that the offset field H_E is positive and the M - H loops is slightly right shifted, whereas, in that with $H_{\text{FC}} = 50$ kOe the offset field, H_E , is negative. The two H_E values (positive/negative exchange bias) with two different initial FC values are marked in Fig. 2.

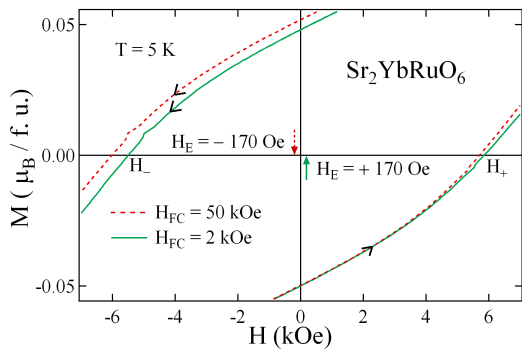


Figure 2: Expanded portion of the magnetization loops in cooling fields (H_{FC}) of 2 kOe and 50 kOe in $\text{Sr}_2\text{YbRuO}_6$ at 5 K. Note that the exchange bias field H_E in the two cases have opposite signs.

To explore the effect of H_{FC} on H_E , M - H loops were later traced between ± 15 kOe as a function of H_{FC} at two tem-

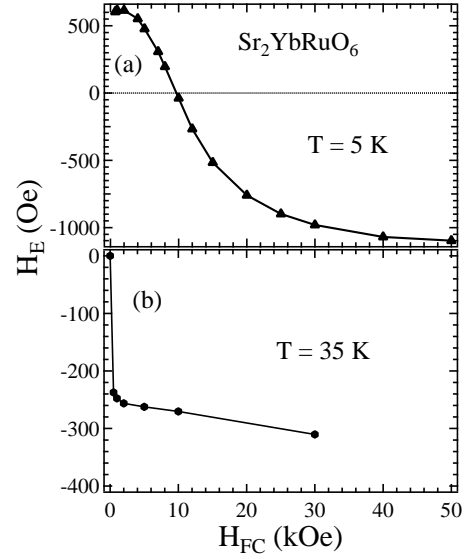


Figure 3: Dependence of the exchange bias field (H_E) on the initial cooling field (H_{FC}) in $\text{Sr}_2\text{YbRuO}_6$ at (a) 5 K and (b) 35 K.

peratures, 5 K (i.e., well below the compensation temperature T_{comp} of 33.5 K) and 35 K ($> T_{\text{comp}}$) as a function of the cooling field (H_{FC}). The H_E values obtained from such measurements are shown in Figs. 3(a) and 3(b). At 5 K (cf. Fig 3(a)), H_E is positive for low cooling fields. As the value of H_{FC} increases, H_E monotonically decreases, crossing zero at $H_{\text{FC}} \sim 10$ kOe, and thereafter moves towards a saturated negative value, above H_{FC} of 30 kOe. On the other hand, at $T = 35$ K, one observes only the usual negative H_E values in low as well as high cooling fields (cf. Fig. 3(b)). We also noted that a given H_E value depends on the extent of the limit set on the cyclic field (e.g. ± 15 kOe for data in Fig. 3(a)), however the trend of change in sign of H_E as a function of H_{FC} (at 5 K) and its approach to saturation (above T_{comp} at 35 K) does not depend on the choice of the limit set on the cycling field.

The temperature variation study of the EB effect was performed on the hysteresis loops measured between ± 15 kOe in two cooling fields, 50 kOe and 2 kOe. H_E values obtained from the hysteresis loops at different temperatures are shown in Fig. 4(a) along with the half width of the hysteresis loops, which is often termed as the effective coercive field, $H_c^{\text{eff}} = -(H_- - H_+)/2$, in Fig 4(b) for comparison²⁸. We note first in Fig. 4(b) that just as in the two insets of Fig. 1 for 5 K, the width of hysteresis loop does not imbibe any dependence on the initial cooling field values at all temperatures. $H_c^{\text{eff}}(T)$ in Fig. 4(b) displays a minimum at about 37 K (see, also, inset of Fig. 4(b)), which is unexpectedly above the compensation temperature of 33 K in low fields (cf. Fig. 1)¹⁸. T_{comp} values had earlier been noted¹⁸ to decrease with large enhancement in H ($H > 2$ kOe) in this system. As regards the temperature dependence of EB field in Fig. 4(a), the H_E values for $H_{\text{FC}} = 50$ kOe maintained the usual negative sign over entire temperature range on warming up from 5 K towards T_C . However, those for $H_{\text{FC}} = 2$ kOe show a sign reversal from positive to

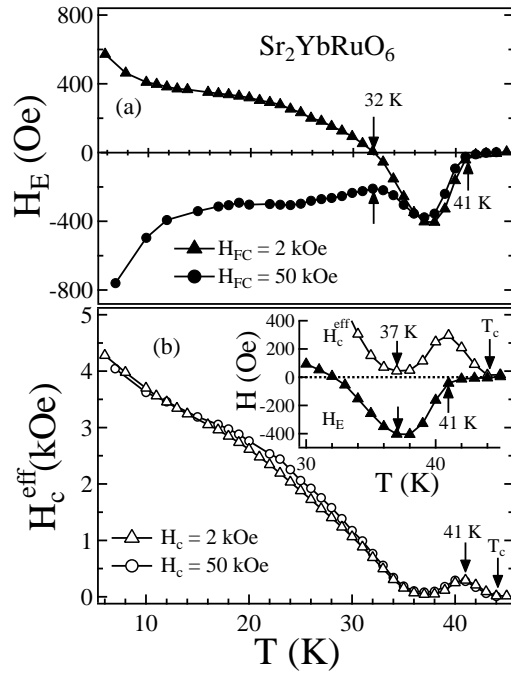


Figure 4: Temperature variation of (a) the exchange bias field (H_E) and (b) the effective coercive field (H_c^{eff}) in cooling fields (H_{FC}) of 50 kOe and 2 kOe. The inset panel in Fig. 4(b) shows H_E (closed symbols) and H_c^{eff} (open symbols) in the temperature range 30–45 K for $H_{FC} = 2$ kOe

negative values at about 32 K, which is close to the T_{comp} value in Fig. 1. The latter behaviour appears to echo the change in sign of H_E reported across T_{comp} in the admixed rare earth intermetallic $\text{Nd}_{0.75}\text{Ho}_{0.25}\text{Al}_2$ ¹⁷ and other similar systems which imbibe compensation behaviour¹⁶. However, the sense of sign change in $\text{Sr}_2\text{YbRuO}_6$ is phase reversed *vis. a vis.* that in $\text{Nd}_{0.75}\text{Ho}_{0.25}\text{Al}_2$. The $|H_E|$ values for $H_{FC} = 50$ kOe reach a local minimum near T_{comp} (*cf.* Fig. 4(a)). Above about 35 K, the two sets of $H_E(T)$ values (in Fig. 4(a)) overlap, thereby implying their independence of the initial field cool history. The $|H_E(T)|$ values can be seen to reach a local maximum at 37 K, where $H_c^{\text{eff}}(T)$ is minimum. This correspondence between $H_c^{\text{eff}}(T)$ and $|H_E(T)|$ is also very different from the trend seen in the admixed rare-earth intermetallic and the magnetic multilayer systems^{7,16,17} across the respective T_{comp} values. In

the latter varieties of systems^{16,17,28}, the width of the hysteresis loop nearly collapses at T_{comp} , and the exchange bias also tends to disappear.

In consonance with the vanishing of the magnetization at the compensation temperature, Fig. 4(a) also shows that while cooling down $|H_E(T)|$ surfaces up only on cooling field below 41 K, the temperature at which $H_c^{\text{eff}}(T)$ shows a local maximum. It has been argued earlier¹⁸ that the decrease in magnetization below 41 K signals the onset of turnaround in the orientation of local moments of Ru due to coming in the play of the D–M interaction. We believe that subtle differences between the details of correspondence between the $H_c^{\text{eff}}(T)$ and $H_E(T)$ occurring in $\text{Sr}_2\text{YbRuO}_6$ *vis. a vis.* other systems, where compensation behavior has been noted, are a consequence of competition and interplay between three components in $\text{Sr}_2\text{YbRuO}_6$ (*viz.* (i) residual ferromagnetism from Ru and (ii) residual magnetisation from Yb moments, and (iii) reorientation in Ru and Yb moments triggered by the D–M interaction) instead of the usual competition between the two antiferromagnetically linked components in other systems²⁹.

To summarize, we have shown that an antiferromagnetic double perovskite compound $\text{Sr}_2\text{YbRuO}_6$ comprising magnetic moments residing on rare earth and transition elements exhibits a large variety in exchange bias behaviour. The dependence of EB field on the cycling field, its sign change on moving across T_{comp} , dependence of EB on the cooling field, etc. are attributes, which have been noted earlier in different magnetic multi-components systems, in the forms of multilayer, coated nano particles, etc.¹ as well as in single component systems, like, admixed rare earth intermetallics^{16,17}, transition metal oxides^{13,14,19}, etc. Our above findings that an antiferromagnetic double perovskite compound $\text{Sr}_2\text{YbRuO}_6$, exhibits the entire spectrum of exchange bias behaviour in the same compound, underscores the importance and novelty of oxide compounds comprising rare earth and transition metal ions. The exchange bias field of either sign can be selected in the $\text{Sr}_2\text{YbRuO}_6$ compound in a predetermined manner by choosing the cooling field and/or changing the temperature. The attribute of easy tuning of the exchange bias calls for further explorations of this behaviour in single crystal and/or oriented thin film form to gain deeper insight into the microscopic basis of the origin of exchange bias and its variation with field/temperature and thermomagnetic history in the compounds crystallizing in double perovskite structure.

- ¹ J. Nogues and I. K. Schuller, J. Magn. Magn. Mater. **192**, 203 (1999).
- ² W. H. Meiklejohn and C. P. Bean, Phys. Rev. **102**, 1413 (1956).
- ³ C. Tsang, R. E. Fontana, T. Lin, D. Heim, V. S. Speriosu, B. A. Gurney, and M. L. Williams, IEEE Trans. Magn. **30**, 3801 (1994).
- ⁴ I. L. Prejbeanu, M. Kerekes, R. C. Sousa, H. Sibuet, O. Redon, B. Dieny, and J. P. Nozières, J. Phys.: Condens. Matter **19**, 165218 (2007).
- ⁵ Y. T. Chen, S. U. Jen, Y. D. Yao, J. M. Wu, J. H. Liao and T. B. Wu, J. Alloys Compounds **448**, 59 (2008).

- ⁶ H. Fuke, Y. Kamiguchi, S. Hashimoto, T. Funiyama, K. Saito, H. Iwasaki and M. Sahashi, US Patent No 6057049 (2004)
- ⁷ J. Nogués, D. Lederman, T. J. Moran and I. K. Schuller, Phys. Rev. Lett. **76**, 4624 (1996).
- ⁸ C. Leighton, J. Nogués, B. J. Jönsson-Akerman and I. K. Schuller, Phys. Rev. Lett. **84**, 3466 (2000).
- ⁹ T. Gredig, I. N. Krivorotov, P. Eames and E. D. Dahlberg, Appl. Phys. Lett. **81**, 1270 (2002).
- ¹⁰ F. Radu, M. Etzkorn, R. Siebrecht, T. Schmitte, K. Westerholt and H. Zabel, Phys. Rev. B **67**, 134409 (2003).

- ¹¹ M. Ali, P. Adie, C. H. Marrows, D. Greig, B. J. Hickey and R. L. Stamps, *Nature Mater.* **6**, 70 (2007).
- ¹² J. T. Kohlhepp, H. Wieldraaijer and W. J. M de Jonge, *J. Mater. Res.* **22**, 569 (2007).
- ¹³ S. Karmakar, S. Taran, E. Bose and B. K. Chaudhuri, *Phys. Rev B* **77**, 144409 (2008).
- ¹⁴ Y.-k. Tang, Y. Sun and Z.-h. Cheng, *Phys. Rev B* **73**, 174419 (2006).
- ¹⁵ X. H. Chen, K. Q. Wang, P. H. Hor, Y. Y. Xue and C. W. Chu, *Phys. Rev B* **72**, 054436 (2005).
- ¹⁶ P. D. Kulkarni, S. Venkatesh, A. Thamizhavel, V. C. Rakhecha, S. Ramakrishnan and A. K. Grover, *IEEE Trans.* **45**, 2902 (2009).
- ¹⁷ P. D. Kulkarni, A. Thamizhavel, V. C. Rakhecha, A. K. Nigam, P. L. Paulose, S. Ramakrishnan and A. K. Grover, *Euro Phys. Lett.* **86**, 47003 (2009).
- ¹⁸ R. P. Singh and C. V. Tomy, *J. Phys.: Condensed Matter* **20**, 23520 (2008).
- ¹⁹ R. P. Singh, S. Marik, C. V. Tomy and A. K. Grover, *Proc. Annual DAE SSP Symposium*, **54**, 1085 (2009).
- ²⁰ R. P. Singh, Ph.D. Thesis, Indian Institute of Technology Bombay, Mumbai, India, 2010.
- ²¹ P. C. Donohue and E. L. McCann, *Mater. Res. Bull.* **12**, 519 (1977).
- ²² P. D. Battle and W. J. Macklin, *J. of Solid State Chem.* **52**, 138 (1984).
- ²³ Y. Doi and Y. Hinatsu, *J. Phys.: Condens. Matter* **11**, 4813 (1999).
- ²⁴ L. D. Tung, M. R. Lee, G. Balakrishnan, and D. McK. Paul, *Phys. Rev. B* **75**, 104404 (2007).
- ²⁵ I. Dzyaloshinsky, *J. Phys. Chem. Solids* **4**, 241 (1958).
- ²⁶ T. Moriya, *Phys. Rev.* **120**, 91 (1960).
- ²⁷ R. P. Singh and C. V. Tomy, *Phys. Rev. B* **78**, 024432 (2008).
- ²⁸ D. J. Webb, A. F. Marshall, Z. Sun, T. H. Geballe and R. M. White, *IEEE Trans. Magn.* **24**, 588 (1988).
- ²⁹ Y. Ren, T. T. M. Palstra, D. I. Khomskii, E. Pellegrin, A. A. Nugroho, A. A. Menovsky and G. A. Sawatzky, *Nature* **396**, 441 (1998).